

Article

Optical response of an interacting polaron gas in strongly polar crystals

Serghei Klimin ¹*, Jacques Tempere ^{1,2}, Jozef T. Devreese ¹, Cesare Franchini ^{3,4} and Georg Kresse ³

¹ TQC, Universiteit Antwerpen, Universiteitsplein 1, B-2610 Antwerpen, Belgium

² Lyman Laboratory of Physics, Harvard University, Cambridge, Massachusetts MA 02138, USA

³ Faculty of Physics, Computational Materials Physics, University of Vienna, Vienna A-1090, Austria

⁴ Dipartimento di Fisica e Astronomia, Università di Bologna, 40127 Bologna, Italy

* Correspondence: sergei.klimin@uantwerpen.be

Abstract: Optical conductivity of an interacting polaron gas is calculated within an extended random phase approximation which takes into account mixing of collective excitations of the electron gas with LO phonons. This mixing is important for the optical response of strongly polar crystals where the static dielectric constant is rather high, as in the case of strontium titanate. The present calculation sheds light on unexplained features of experimentally observed optical conductivity spectra in *n*-doped SrTiO₃. These features appear to be due to dynamic screening of the electron-electron interaction by polar optical phonons and hence do not require additional mechanisms for their explanation.

Keywords: polaron; many-polaron systems; optical response

1. Introduction

Polaron manifestations in the optical response of polar crystals, such as complex oxides and high- T_c superconductors are the subject of intense investigations [1–7] (for a review, see also [8,9]). Several features in the infrared optical absorption spectra of complex oxides have been associated with large polarons [10] or with a mixture of large and small polarons [11]. The analysis in those papers was performed using a single-polaron model, so that the concentration dependence of the optical-absorption spectra could not properly take into account many-polaron effects.

The many-body theory of the optical absorption of a gas of interacting polarons [12,13] allows one to study the density dependence of the optical-absorption spectra. The calculation [12] was performed in the single-branch approximation for LO phonons. In Ref. [13], the optical conductivity of *n*-doped SrTiO₃ was calculated accounting for the electron-phonon interaction with multiple LO-phonon branches. The calculations of the optical conductivity of a weak-coupling polaron gas [12,13] compare fairly well with the experimental data [1,2] and therefore confirm the contribution of large polarons in the optical response. Strontium titanate represents an especially interesting case due to its unique features, particularly a high static dielectric constant at low temperatures and essentially nonparabolic shape of the conduction band which consists of three subbands. This requires a treatment of the optical conductivity beyond the frequently used lowest-order perturbation approximation.

The first-principle methods are powerful for the theoretical study of both equilibrium and response properties of polarons. At present, *ab initio* calculations of the polaron band energies are developed, for example, in Refs. [14–18]. In the present work, we consider a complementary semianalytic approach, which has its own advantages. First, it is much less time- and memory-consuming for computation.

Second, more important, it allows sometimes a clear physical interpretation of features of obtained spectra, as they follow from a used model.

The present work is focused on the many-polaron optical response in strongly polar crystals like SrTiO_3 . The strong polarity means that the ratio of the static and high-frequency dielectric constant is large: $\varepsilon_0/\varepsilon_\infty \gg 1$. This does not necessarily lead to a high electron-phonon coupling constant: in strontium titanate the effective coupling constant $\alpha \approx 2$ as determined in [13]. Even in this moderate-coupling case, electron collective excitations (attributed to plasmons only in the long-wavelength limit) are substantially mixed with LO phonons [19] and therefore can result in a non-trivial spectrum of the optical conductivity. Therefore, in this paper, we determine the optical conductivity of a many polaron gas taking into account mixing of phonons and electron collective excitations in the total dielectric function of the electron-phonon system, and taking also into account the multi-subband structure of the conductivity band. The method is applied to n -doped strontium titanate.

2. Many-polaron optical conductivity

We consider an electron-phonon system with the following Hamiltonian in the momentum representation:

$$H = \sum_{\lambda} \sum_{\mathbf{k}} \varepsilon_{\lambda}(\mathbf{k}) \sum_{\sigma=\pm 1/2} a_{\mathbf{k},\sigma,\lambda}^{\dagger} a_{\mathbf{k},\sigma,\lambda} + \sum_{\mathbf{q},j} \hbar \omega_{\mathbf{q},j} \left(b_{\mathbf{q},j}^{\dagger} b_{\mathbf{q},j} + \frac{1}{2} \right) + \sum_{\mathbf{q},j} V_{\mathbf{q},j} (b_{\mathbf{q},j} + b_{-\mathbf{q},j}^{\dagger}) \sum_{\lambda} \sum_{\mathbf{k}} \sum_{\sigma=\pm 1/2} a_{\mathbf{k}+\mathbf{q},\sigma,\lambda}^{\dagger} a_{\mathbf{k},\sigma,\lambda}, \quad (1)$$

where $\varepsilon_{\lambda}(\mathbf{k})$ is the electron energy with the momentum $\hbar\mathbf{k}$ in the λ -th subband of the conduction band, $a_{\mathbf{k},\sigma,\lambda}^{\dagger}$ and $a_{\mathbf{k},\sigma,\lambda}$ are, respectively, creation and annihilation fermionic operators for an electron with the spin projection σ , $\omega_{\mathbf{q},j}$ is the phonon frequency for the momentum $\hbar\mathbf{q}$ and the phonon branch j , $b_{\mathbf{q},j}^{\dagger}$ and $b_{\mathbf{q},j}$ are, respectively, phonon creation and annihilation operators. The electron-phonon interaction amplitudes $V_{\mathbf{q},j}$ are used here neglecting their possible dependence on the electron momentum and the subband number. This dependence can only be non-negligible when high-energy electrons bring an important contribution to the many-polaron response, which is not believed to be the case for strontium titanate.

For the many-polaron optical response, we start from the Kubo formula,

$$\sigma_{xx}(\Omega) = \frac{1}{Vz} \left[\frac{1}{\hbar} \int_0^{\infty} dt e^{izt} \langle [J_x(t), J_x(0)] \rangle + i\mathcal{Z} \right] \quad (2)$$

$$\left(\beta = \frac{1}{k_B T}, z = \Omega + i\delta, \delta \rightarrow +0 \right)$$

where V is the system volume, e is the electronic charge, and the constant \mathcal{Z} is determined by the current-current correlator:

$$\mathcal{Z} = \frac{1}{\hbar} \int_0^{\hbar\beta} d\tau \langle J_x(\tau) J_x(0) \rangle, \quad (3)$$

and J_x is the current operator determined by:

$$J_x = -ev_x = -\frac{e}{\hbar} \sum_{\lambda} \sum_{\mathbf{k}} \sum_{\sigma=\pm 1/2} \frac{\partial \varepsilon_{\lambda}(\mathbf{k})}{\partial k_x} a_{\mathbf{k},\sigma,\lambda}^{\dagger} a_{\mathbf{k},\sigma,\lambda}. \quad (4)$$

The constant \mathcal{Z} can be calculated explicitly. Substituting (4) to (3) and applying commutation relations for second quantization operators, we arrive at the result,

$$\mathcal{Z} = \frac{e^2}{\hbar^2} \sum_{\lambda} \sum_{\mathbf{k}} \sum_{\sigma} \frac{\partial^2 \varepsilon_{\lambda}(\mathbf{k})}{\partial k_x^2} f_{\mathbf{k},\sigma,\lambda} \quad (5)$$

with the distribution function of the electrons,

$$f_{\mathbf{k},\sigma} = \left\langle a_{\mathbf{k},\sigma,\lambda}^\dagger a_{\mathbf{k},\sigma,\lambda} \right\rangle. \quad (6)$$

Next, we perform twice the integration by parts in the integral over time in (2) and introduce the force operator,

$$\frac{\partial J_x(t)}{\partial t} \equiv e\mathcal{F}_x(t). \quad (7)$$

which is explicitly given by the expression:

$$\mathcal{F}_x = \frac{i}{\hbar} \sum_{\mathbf{q},j} V_{\mathbf{q},j} \left(b_{\mathbf{q},j} + b_{-\mathbf{q},j}^\dagger \right) \hat{B}_{\mathbf{q}}, \quad (8)$$

with

$$\hat{B}_{\mathbf{q}} \equiv \frac{1}{\hbar} \sum_{\lambda} \sum_{\mathbf{k}} \sum_{\sigma} \left(\frac{\partial \varepsilon_{\lambda}(\mathbf{k} + \mathbf{q})}{\partial k_x} - \frac{\partial \varepsilon_{\lambda}(\mathbf{k})}{\partial k_x} \right) a_{\mathbf{k},\sigma,\lambda}^\dagger a_{\mathbf{k},\sigma,\lambda} \quad (9)$$

After these two integrations by parts, the Kubo formula is equivalently rewritten through the force-force correlation function,

$$\sigma_{xx}(\Omega) = \frac{e^2}{\hbar V (\Omega + i\delta)^3} \int_0^\infty dt e^{-\delta t} \left(e^{i\Omega t} - 1 \right) \langle [\mathcal{F}_x(t), \mathcal{F}_x(0)] \rangle + \frac{i}{V} \frac{\mathcal{Z}}{\Omega + i\delta}. \quad (10)$$

Next, we consider the weak-coupling regime. The weak-coupling optical conductivity can be expressed in the memory-function form, as, e. g., in Refs. [20,21]:

$$\sigma_{xx}(\Omega) = \frac{i}{V} \frac{\mathcal{Z}}{\Omega + i\delta - \chi(\Omega) / (\Omega + i\delta)}. \quad (11)$$

where the memory function $\chi(\Omega)$ is:

$$\chi(\Omega) = -\frac{i}{\mathcal{Z}} \frac{e^2}{\hbar} \int_0^\infty dt e^{-\delta t} \left(e^{i\Omega t} - 1 \right) \langle [\mathcal{F}_x(t), \mathcal{F}_x(0)] \rangle_0. \quad (12)$$

Here, the averaging $\langle \dots \rangle_0$ is performed with the Hamiltonian of interacting electrons neglecting the electron-phonon interaction.

We can transform the memory function in an explicitly tractable expression substituting (8) and (9) in (12). Thus we obtain the resulting memory function:

$$\chi(\Omega) = \frac{2e^2}{\hbar^3 \mathcal{Z}} \sum_{\mathbf{q},j} |V_{\mathbf{q},j}|^2 \int_0^\infty dt e^{-\delta t} \left(e^{i\Omega t} - 1 \right) \text{Im} \left[T^* (\omega_{\mathbf{q},j}, t) \left\langle \hat{B}_{\mathbf{q}}(t) \hat{B}_{\mathbf{q}}^\dagger \right\rangle_0 \right]. \quad (13)$$

where $T(\omega_{\mathbf{q},j}, t)$ is the phonon Green's function:

$$T(\omega_{\mathbf{q},j}, t) = (1 + \bar{n}_{\mathbf{q},j}) e^{i\omega_{\mathbf{q},j} t} + \bar{n}_{\mathbf{q},j} e^{-i\omega_{\mathbf{q},j} t}. \quad (14)$$

and $\bar{n}_{\mathbf{q},j}$ is the Bose distribution of phonons:

$$\bar{n}_{\mathbf{q},j} = \frac{1}{e^{\beta \hbar \omega_{\mathbf{q},j}} - 1}. \quad (15)$$

The f -sum rule for the optical conductivity reads:

$$\int_{-\infty}^{\infty} \text{Re} \sigma_{xx}(\Omega) d\Omega = \frac{\pi}{2} \frac{\mathcal{Z}}{V}. \quad (16)$$

In the general case the constant \mathcal{Z} can be different from the value $\frac{e^2 N_e}{m_b}$ obtained in Ref. [22], which follows from (5) for a quadratic dispersion.

3. Semianalytic approximations

The optical conductivity of an interacting polaron gas is calculated here within the extended random phase approximation (RPA), as described below. The memory function $\chi(\Omega)$ can be expressed through the polarization function of the electron gas for sufficiently small \mathbf{q} . Thus the RPA can be applied under the assumption that the long-wavelength phonons bring the dominant contribution to the polaron optical response. In this approximation, the band energy $\varepsilon_\lambda(\mathbf{k})$ which enters the operator $\hat{B}_\mathbf{q}$ is expanded in powers of the momentum as $\varepsilon_\lambda(\mathbf{k}) = \hbar^2 k^2 / 2m_{b,\lambda} + O(k^4)$. In SrTiO₃, the band mass obtained within the tight-binding analytic fit as described in Appendix A appears isotropic with the same value $m_b \approx 0.72m_e$ (where m_e is the electron mass in vacuum) for all three subbands of the conduction band. Thus the memory function for the optical conductivity is approximated by the expression:

$$\chi(\Omega) = \frac{2e^2}{3\hbar m_b^2 \mathcal{Z}} \sum_{\mathbf{q},j} |V_{\mathbf{q},j}|^2 q^2 \int_0^\infty dt e^{-\delta t} (e^{i\Omega t} - 1) \text{Im} \left[T^* (\omega_{\mathbf{q},j}, t) \langle \rho_{\mathbf{q}}(t) \rho_{\mathbf{q}}^\dagger \rangle_0 \right], \quad (17)$$

where $\rho_{\mathbf{q}} = \sum_{\mathbf{k},\sigma,\lambda} a_{\mathbf{k}+\mathbf{q},\sigma,\lambda}^\dagger a_{\mathbf{k},\sigma,\lambda}$ is the Fourier component of the electron density. Note that below, when calculating the density-density correlation function, we do not perform this expansion.

Here, we use the Fröhlich interaction amplitudes with the partial coupling constants α_j for the j -th phonon branch:

$$V_{\mathbf{q},j} = \frac{\hbar\omega_{L,j}}{q} \left(\frac{4\pi\alpha_j}{V} \right)^{1/2} \left(\frac{\hbar}{2m_b\omega_{L,j}} \right)^{1/4}. \quad (18)$$

In terms of Green's functions, the memory function (17) takes the form:

$$\begin{aligned} \chi(\Omega) = & \sum_j \frac{\alpha_j \hbar \omega_{L,j}^2 e^2}{6\pi^2 m_b^2 \mathcal{Z}} \left(\frac{\hbar}{2m_b\omega_{L,j}} \right)^{1/2} \\ & \times \int d\mathbf{q} \{ \mathcal{G}(\mathbf{q}, \Omega - \omega_{L,j}) + \mathcal{G}^*(\mathbf{q}, -\Omega - \omega_{L,j}) - \mathcal{G}(\mathbf{q}, -\omega_{L,j}) - \mathcal{G}^*(\mathbf{q}, -\omega_{L,j}) \\ & + \frac{1}{e^{\beta\hbar\omega_{L,j}} - 1} [G^R(\mathbf{q}, \Omega - \omega_{L,j}) + (G^R(\mathbf{q}, -\Omega - \omega_{L,j}))^* \\ & - G^R(\mathbf{q}, -\omega_{L,j}) - (G^R(\mathbf{q}, -\omega_{L,j}))^*] \}. \end{aligned} \quad (19)$$

with

$$\mathcal{G}(\mathbf{q}, \Omega) \equiv -i \int_0^\infty e^{i\Omega t} \langle \rho_{\mathbf{q}}(t) \rho_{-\mathbf{q}}(0) \rangle_0 dt, \quad (20)$$

$$G^R(\mathbf{q}, \Omega) \equiv -i \int_0^\infty e^{i\Omega t} \langle [\rho_{\mathbf{q}}(t), \rho_{-\mathbf{q}}(0)] \rangle_0 dt. \quad (21)$$

In Ref. [13], the Green's functions were calculated within the RPA for an electron gas. Here, we apply the RPA extended for an interacting electron-phonon system, which leads to a formula structurally similar to that obtained within RPA, but with a different (momentum and frequency dependent) electron-electron interaction matrix element:

$$\frac{4\pi e^2}{\varepsilon_\infty q^2} \rightarrow \frac{4\pi e^2}{\varepsilon_L(\mathbf{q}, \omega) q^2}, \quad (22)$$

with the dielectric function of the lattice $\varepsilon_L(\mathbf{q}, \omega)$, which describes the dynamic lattice polarization. In the present calculation, we use the model of independent oscillators [23,24] which correspond to the LO and TO phonon modes:

$$\varepsilon_L(\mathbf{q}, \Omega) = \varepsilon_\infty \prod_{j=1}^n \left(\frac{\Omega^2 - \omega_{Lj}^2(\mathbf{q})}{\Omega^2 - \omega_{Tj}^2(\mathbf{q})} \right). \quad (23)$$

The extended RPA thus takes into account the dynamic screening of the Coulomb electron-electron interaction by the lattice polarization. The resulting retarded density-density Green's function is:

$$G^R(\mathbf{q}, \Omega) = \frac{\hbar V P^{(1)}(\mathbf{q}, \Omega)}{1 - \frac{4\pi e^2}{\varepsilon_L(\mathbf{q}, \Omega)q^2} P^{(1)}(\mathbf{q}, \Omega)}, \quad (24)$$

where $P^{(1)}(\mathbf{q}, \Omega)$ is the Lindhard polarization function,

$$P^{(1)}(\mathbf{q}, \Omega) = \frac{1}{V} \sum_{\mathbf{k}, \sigma, \lambda} \frac{f_F(\varepsilon_\lambda(\mathbf{k} + \mathbf{q}) - \mu_\lambda) - f_F(\varepsilon_\lambda(\mathbf{k}) - \mu_\lambda)}{\hbar\Omega + \varepsilon_\lambda(\mathbf{k} + \mathbf{q}) - \varepsilon_\lambda(\mathbf{k}) + i0^+} \quad (25)$$

with the Fermi distribution function $f_F(\varepsilon)$:

$$f_F(\varepsilon) = \frac{1}{e^{\beta(\varepsilon - \mu)} + 1}. \quad (26)$$

The function $\mathcal{G}(\mathbf{q}, \Omega)$ is obtained from $G^R(\mathbf{q}, \Omega)$ using the analytic identity,

$$(1 - e^{-\beta\hbar\Omega}) \operatorname{Im} \mathcal{G}(\mathbf{q}, \Omega) = \operatorname{Im} G^R(\mathbf{q}, \Omega), \quad (27)$$

and then the Kramers-Kronig dispersion relation for $\operatorname{Re} \mathcal{G}(\mathbf{q}, \Omega)$.

For a comparison with experiment, the Green's functions are calculated here accounting for damping within the Mermin-Lindhard approach [25–28] (where the damping is introduced in such a way to conserve the local electron number). This leads to the modification of the retarded density-density Green's function as follows:

$$G^R(\mathbf{q}, \Omega) \rightarrow G_M^R(\mathbf{q}, \Omega, \gamma) = G^R(\mathbf{q}, \Omega + i\gamma) \frac{\Omega + i\gamma}{\Omega + i\gamma \frac{G^R(\mathbf{q}, \Omega + i\gamma)}{G^R(\mathbf{q}, 0)}}. \quad (28)$$

where γ is the phenomenological damping factor. The values of γ found in the literature are of the order of the Fermi energy of electrons [29,30]. Here, γ is a fitting parameter of the same order of magnitude (the *only* fitting parameter which is in fact used here). The calculation is performed with the values $\gamma = 1.2\varepsilon_{F,1}$ for $T = 7\text{ K}$ and $\gamma = 2\varepsilon_{F,1}$ for $T = 300\text{ K}$. It should be noted that the results appear to be only slightly sensitive to chosen values of γ .

The calculation of the Green's functions for non-parabolic bands requires knowledge of overlap integrals [31] for the Coulomb and electron-phonon interactions, which is not yet reliably known and needs a microscopic calculation. In order to simplify the computation keeping main features of the non-parabolic band dispersion, we perform two approximations.

First, we apply the density-of-states approach already successfully used in Ref. [32]. The approximation consists in the replacement of the true band energy $\varepsilon_\lambda(\mathbf{k})$ by the model isotropic band energy $\varepsilon_\lambda(k)$ which provides *the same density of states* as that for the true band energy $\varepsilon_\lambda(\mathbf{k})$. The density of states $\nu_\lambda(E)$ in the λ -th subband of the conductivity band is determined using the carrier density:

$$n_\lambda = \frac{1}{4\pi^3} \int d\mathbf{k} f(\varepsilon_\lambda(\mathbf{k}) - \mu) = \int_{\varepsilon_{\lambda, \min}}^{\varepsilon_{\lambda, \max}} f(E - \mu_\lambda) \nu_\lambda(E) dE. \quad (29)$$

where $\varepsilon_{\lambda,\min} = \varepsilon_{\lambda}(\mathbf{k})|_{k=0}$. The model isotropic band energy dispersion is determined through the function

$$k_{\lambda}(E) = \left(3\pi^2 \int_{\varepsilon_{\lambda,\min}}^E \nu_{\lambda}(\varepsilon) d\varepsilon \right)^{1/3}, \quad (30)$$

so that $\varepsilon_{\lambda}(k)$ is the inverse function to this $k_{\lambda}(E)$.

Second, $\varepsilon_{\lambda}(k)$ appears to be approximately parabolic in a rather wide range of the momentum. Therefore we assume the parabolic conduction band for the calculation of Green's functions but with the density-of-states effective masses m_{λ} determined through the density of states from the condition that the low-momentum expansion of the polarization function $P^{(1)}(\mathbf{q}, \Omega)$ with the dispersion $\varepsilon_{\lambda}(k)$ coincides with that for a parabolic band dispersion with the mass m_{λ} . This gives us the expression:

$$m_{\lambda} = 3\pi^4 n_{\lambda} \left(\int_{\varepsilon_{\lambda,\min}}^{\varepsilon_{\lambda,\max}} \frac{\beta e^{\beta(E-\mu)}}{(e^{\beta(E-\mu)} + 1)^2} \frac{k_{\lambda}^4(E)}{\nu_{\lambda}(E)} dE \right)^{-1}. \quad (31)$$

In the zero-temperature limit, m_{λ} is analytically expressed through the density of states at the Fermi energy $\varepsilon_{F,\lambda}$:

$$m_{\lambda} = \pi^2 \frac{\nu_{\lambda}(\varepsilon_{F,\lambda})}{k_{F,\lambda}}. \quad (32)$$

As mentioned above, this approximation is not a series expansion of the band energy near the band bottom, and hence the density-of-states mass m_{λ} does not coincide with the band effective mass m_b . An approach which involves the effective band mass and the density-of-states band mass has been used also in Ref. [13]. Here, the density-of-states band mass is determined in a more rigorous way, effectively accounting for the realistic band structure of a crystal, electron density and temperature, as can be seen from (31).

4. Application to SrTiO₃

The approach described above is focused mainly on crystals with a high ratio $\varepsilon_0/\varepsilon_{\infty}$ like strontium titanate, where it can reveal specific features related to the high polarizability. In the previous treatment of the many-polaron optical conductivity in doped SrTiO₃ [13], the pronounced peak for $\hbar\Omega \sim 130$ meV at a relatively low temperature remains unexplained. It was suggested in [13] that it might be provided by other (non-polaron) mechanisms, for example, the small-polaron and mixed-polaron [33] channels for the optical response. As we show below, additional mechanisms are not necessary for the explanation of this 130-meV feature.

The numeric results for the many-polaron optical conductivity are shown in Fig. 1. In the computation, the following set of electron band and phonon material parameters is used. The conduction band shape is simulated by the analytic tight-binding fit as described in Ref. [34] and here in Appendix A. The optimal values for this analytic approximation are the diagonal matrix elements t_{δ}, t_{π} corresponding to the recent results of the microscopic calculation [35] using the GW method [36]: $t_{\delta} = 54.2$ meV, $t_{\pi} = 490.9$ meV, and the band splitting parameters from Ref. [34] $\xi = 18.8$ meV, $D = 2.2$ meV. The optical-phonon energies at the Brillouin zone center of SrTiO₃ are taken from the experimental data of Ref. [2], the same as described in Ref. [13]. Also the direct TO-phonon optical response has been included in the figure in the same way as in Ref. [13]. It is represented by sharp peaks in the low-energy part of the optical conductivity spectrum.

The calculated many-polaron optical conductivity in SrTiO₃ is compared with the experimental data of Ref. [2] for two temperatures: $T = 7$ K and $T = 300$ K and for several values of the carrier concentration. Also the earlier calculation the optical conductivity [13] is reproduced in the figure. As can be seen from the low-temperature results shown in the left-hand panels of the figure, the 130-meV peak and the dip at $\hbar\Omega \sim 200$ meV (corresponding to twice the highest-energy LO phonon

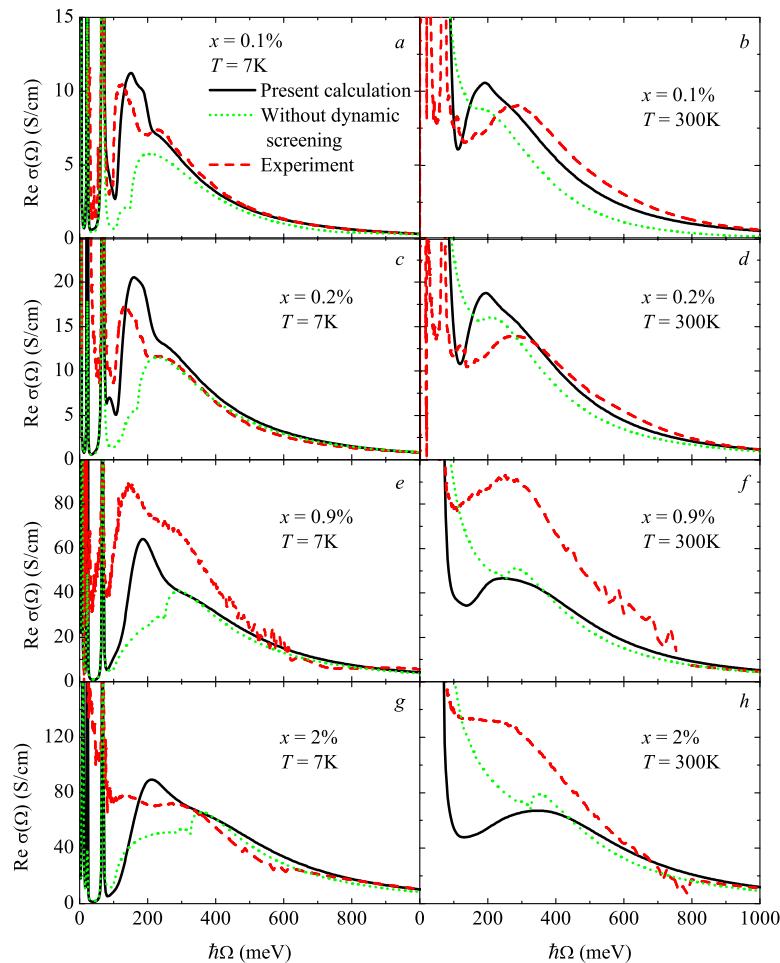


Figure 1. Many-polaron optical conductivity of n -doped SrTiO_3 in the mid-infrared frequency range for several values of the doping x and two temperatures (the parameters are indicated in the figure), corresponding to the experimental conditions of Ref. [2]. The calculated spectra (solid curves) are compared with the experimental data (dashed curves). Dotted curves show the results of Ref. [13].

mode ion strontium titanate) experimentally observed at the low temperature and at relatively low concentrations are fairly well revealed in the calculated spectra of the optical conductivity.

The obtained expression (24) for the retarded density-density Green's function gives us a transparent explanation of the shape of the optical conductivity spectrum, which is more complicated than in the absence of the dynamic screening. The Green's functions enter the memory function (19) with the arguments $(\pm\Omega - \omega_{L,j})$. Therefore the dynamically screened electron-electron interaction matrix element (22) contains poles, in particular, at $\Omega = 2\omega_{L,j}(\mathbf{q})$, which result in dips of the optical conductivity at these frequencies. The most significant contribution to the dips comes from the highest LO phonon energy $\hbar\omega_{L,3}|_{q=0} \approx 98$ meV. This feature is visible in both the measured and calculated optical conductivity spectra. The part of the spectrum below $2\omega_{L,3}$ constitutes the aforesaid 130-meV peak. The other part of the spectrum, above $2\omega_{L,3}$, contains the “plasmon-phonon” peak provided by the response due to undamped plasmons [12,13].

5. Conclusions

In the present work, we revisit the optical response of a polaron gas in complex polar crystals using the random phase approximation extended for an interacting electron-phonon system. This extension results in a modified many-polaron optical conductivity with an effective electron-electron interaction accounting for the dynamic screening by LO phonons. For a more realistic calculation

relevant for comparison with experiment for strontium titanate, the phonon dielectric function contains several optical phonon modes that have been identified in SrTiO_3 .

A distinctive low-frequency peak of the many-polaron optical conductivity in a polar medium appears when a crystal is highly polar, $\varepsilon_0/\varepsilon_\infty \gg 1$, which is realized in strontium titanate. As can be seen from the obtained spectra of the optical conductivity, the dynamic screening leads to an appearance of this peak which is close to the experimental “130-meV feature”, except for the highest available density. Moreover, its width and shape asymmetry are remarkably similar to those of the experimental peak, including even fine details such a small kink at the shoulder above the maximum. Also the whole shape of the spectrum at least for the two lower densities is similar to the experimental results, containing both the low-frequency peak and the “plasmon-phonon” peak due to undamped plasmons. This similarity makes the dynamic screening mechanism for the low-frequency peak convincing. As can be seen from the comparison of the results [13] obtained without account of dynamic screening with those of the present work, we have achieved now much better agreement with the experiment remaining completely within a single physical mechanism exploited for the theoretical interpretation of the many-polaron optical response.

There is also a remarkable agreement between the present theory and the experimental results [2] in what concerns the high-frequency dependence of the optical conductivity (in the range $\hbar\Omega \sim 1 \text{ eV}$), achieved without adjustment, using reliable material parameters known from literature. This agreement is in line with experimentally substantiated conclusion [37] that polarons in SrTiO_3 are large rather than small.

Acknowledgments: We thank D. van der Marel for the experimental data on the optical absorption of SrTiO_3 . This work has been supported by the joint FWO-FWF project POLOX (Grant No. I 2460-N36).

Appendix A. Analytic model for the conductivity band in SrTiO_3

For the calculation of the many-polaron response, it is useful to simulate numerical data for the band structure by an analytic expression. Here, we treat the tight-binding expression similarly to Refs. [2,13]. In these works, the matrix Hamiltonian is used for an analytic fit of the band dispersion law:

$$H = 4 \begin{pmatrix} \varepsilon_1(\mathbf{k}) & 0 & 0 \\ 0 & \varepsilon_2(\mathbf{k}) & 0 \\ 0 & 0 & \varepsilon_3(\mathbf{k}) \end{pmatrix} + \frac{1}{2}W, \quad (\text{A1})$$

with the energies

$$\begin{aligned} \varepsilon_1 &= t_\delta \sin^2\left(\frac{a_0 k_x}{2}\right) + t_\pi \sin^2\left(\frac{a_0 k_y}{2}\right) + t_\pi \sin^2\left(\frac{a_0 k_z}{2}\right), \\ \varepsilon_2 &= t_\pi \sin^2\left(\frac{a_0 k_x}{2}\right) + t_\delta \sin^2\left(\frac{a_0 k_y}{2}\right) + t_\pi \sin^2\left(\frac{a_0 k_z}{2}\right), \\ \varepsilon_3 &= t_\pi \sin^2\left(\frac{a_0 k_x}{2}\right) + t_\pi \sin^2\left(\frac{a_0 k_y}{2}\right) + t_\delta \sin^2\left(\frac{a_0 k_z}{2}\right), \end{aligned} \quad (\text{A2})$$

where a_0 is the lattice constant. The matrix W describes the mixing of subbands within the conductivity band. For the cubic phase of SrTiO_3 , counting the band energy from the G point (i. e., dropping a uniform shift of the whole band), W is given by:

$$W = \begin{pmatrix} 0 & \xi & \xi \\ \xi & 0 & \xi \\ \xi & \xi & 0 \end{pmatrix}. \quad (\text{A3})$$

For the tetragonal phase as reported in Ref. [34], the matrix W is:

$$W = \begin{pmatrix} 2D & \xi & \xi \\ \xi & 2D & \xi \\ \xi & \xi & -4D \end{pmatrix}. \quad (\text{A4})$$

1. S. Lupi, P. Maselli, M. Capizzi, P. Calvani, P. Giura, and P. Roy, "Evolution of a Polaron Band through the Phase Diagram of $Nd_{2-x}Ce_xCuO_{4-y}$ ", *Phys. Rev. Lett.* **83**, 4852 (1999).
2. J. L. M. van Mechelen, D. van der Marel, C. Grimaldi, A. B. Kuzmenko, N. P. Armitage, N. Reyren, H. Hagemann, and I. I. Mazin, "Electron-Phonon Interaction and Charge Carrier Mass Enhancement in $SrTiO_3$ ", *Phys. Rev. Lett.* **100**, 226403 (2008).
3. L. Genzel, A. Wittlin, M. Bayer, M. Cardona, E. Schonherr, and A. Simon, "Phonon anomalies and range of superconducting energy gaps from infrared studies of $YBa_2Cu_3O_{7-\delta}$ ", *Phys. Rev. B* **40**, 2170 (1989).
4. P. Calvani, M. Capizzi, S. Lupi, P. Maselli, A. Paolone, and P. Roy, "Polaronic optical absorption in electron-doped and hole-doped cuprates", *Phys. Rev. B* **53**, 2756 (1996).
5. S. Lupi, M. Capizzi, P. Calvani, B. Ruzicka, P. Maselli, P. Dore, and A. Paolone, "Fano effect in the a - b plane of $Nd_{1.96}Ce_{0.04}CuO_{4+y}$: Evidence of phonon interaction with a polaronic background", *Phys. Rev. B* **57**, 1248 (1998).
6. J.-G. Zhang, X.-X. Bi, E. McRae, P. C. Ecklund, B. C. Sales, M. Mostoller, "Optical studies of single-crystal $Nd_{2-x}Ce_xCuO_{4-\delta}$ ", *Phys. Rev. B* **43**, 5389 (1991).
7. C. C. Homes, B. P. Clayman, J. L. Peng, R. L. Greene, "Optical properties of $Nd_{1.85}Ce_{0.15}CuO_4$ ", *Phys. Rev. B* **56**, 5525 (1997).
8. J. T. Devreese and A. S. Alexandrov, *Fröhlich polaron and bipolaron: recent developments*, *Rep. Prog. Phys.* **72**, 066501 (2009).
9. A. S. Alexandrov and J. T. Devreese, *Advances In Polaron Physics* (Springer, 2009).
10. J. T. Devreese and J. Tempere, "Large-polaron effects in the infrared spectrum of high- T_c cuprate superconductors", *Solid State Commun.* **106**, 309 (1998).
11. D. M. Eagles, R. P. S. M. Lobo, and F. Gervais, "Infrared absorption in oxides in the presence of both large and small polarons", *Phys. Rev. B* **52**, 6440 (1995).
12. J. Tempere and J. T. Devreese, "Optical absorption of an interacting many-polaron gas", *Phys. Rev. B* **64**, 104504 (2001).
13. J. T. Devreese, S. N. Klimin, J. L. M. van Mechelen, and D. van der Marel, "Many-body large polaron optical conductivity in $SrTi_{1-x}Nb_xO_3$ ", *Phys. Rev. B* **81**, 125119 (2010).
14. X. Hao, Z. Wang, M. Schmid, U. Diebold, and C. Franchini, "Coexistence of trapped and free excess electrons in $SrTiO_3$ ", *Phys. Rev. B* **91**, 085204 (2015).
15. F. Giustino, "Electron-phonon interactions from first principles", *Rev. Mod. Phys.* **89**, 015003 (2017); Erratum *Rev. Mod. Phys.* **91**, 019901 (2019).
16. W. H. Sio, C. Verdi, S. Poncé, and F. Giustino, "Ab initio theory of polarons: Formalism and applications" *Phys. Rev. B* **99**, 235139 (2019).
17. W. H. Sio, C. Verdi, S. Poncé, and F. Giustino, "Polarons from First Principles, without Supercells" *Phys. Rev. Lett.* **122**, 246403 (2019).
18. M. Reticcioli, U. Diebold, G. Kresse and C. Franchini, "Small Polarons in Transition Metal Oxides", in: W. Andreoni and S. Yip (eds), *Handbook of Materials Modeling* (Springer, Cham, 2019).
19. L. F. Lemmens and J.T.Devreese, "Collective excitations of the polaron-gas", *Solid State Commun.* **14**, 1339 (1974); L. F. Lemmens, F. Brosens, and J. T. Devreese, *ibid.* **17**, 337 (1975).
20. F. M. Peeters and J. T. Devreese, "Impedance function of large polarons: An alternative derivation of the Feynman-Hellwarth-Iddings-Platzman theory", *Phys. Rev. B* **28**, 6051 (1983).
21. G. De Filippis, V. Cataudella, A. de Candia, A. S. Mishchenko, and N. Nagaosa, "Alternative representation of the Kubo formula for the optical conductivity: A shortcut to transport properties", *Phys. Rev. B* **90**, 014310 (2014).
22. J. T. Devreese, L. F. Lemmens, and J. Van Royen, "Sum rule leading to a relation between the effective mass and the optical absorption of free polarons", *Phys. Rev. B* **15**, 1212 (1977).

23. Y. Toyozawa, in: *Polarons in Ionic Crystals and Polar Semiconductors*, North-Holland, Amsterdam (1972), pp. 1 – 27.
24. R. Zheng, T. Taguchi, and M. Matsuura, “Theory of long-wavelength optical lattice vibrations in multinary mixed crystals: Application to group-III nitride alloys”, *Phys. Rev. B* **66**, 075327 (2002).
25. N. D. Mermin, “Lindhard Dielectric Function in the Relaxation-Time Approximation”, *Phys. Rev. B* **1**, 2362 (1970).
26. Yu. V. Arkhipov, A. B. Ashikbayeva, A. Askaruly, A. E. Davletov, and I. M. Tkachenko, “Dielectric function of dense plasmas, their stopping power, and sum rules”, *Phys. Rev. E* **90**, 053102 (2014).
27. G. Röpke, A. Selchow, A. Wierling and H. Reinholz, “Lindhard dielectric function in the relaxation-time approximation and generalized linear response theory”, *Phys. Lett. A* **260**, 365 (1999).
28. M. D. Barriga-Carrasco, “Influence of damping on proton energy loss in plasmas of all degeneracies”, *Phys. Rev. E* **76**, 016405 (2007).
29. M. D. Barriga-Carrasco, “Full conserving dielectric function for plasmas at any degeneracy”, *Laser and Particle Beams* **28**, 307 (2010).
30. K. Morawetz and U. Fuhrmann, “General response function for interacting quantum liquids”, *Phys. Rev. E* **61**, 2272 (2000).
31. M. Yamaguchi, T. Inaoka, and M. Hasegawa, “Electronic excitations in a nonparabolic conduction band of an n-type narrow-gap semiconductor”, *Phys. Rev. B* **65**, 085207 (2002).
32. S. N. Klimin, J. Tempere, J. T. Devreese, J. He, C. Franchini and G. Kresse, “Superconductivity in SrTiO_3 : Dielectric Function Method for Non-Parabolic Bands”, *Journal of Superconductivity and Novel Magnetism* **32**, 2739 (2019).
33. D. M. Eagles, “Theory of Transitions from Large to Nearly-Small Polarons, with Application to Zr-Doped Superconducting SrTiO_3 ”, *Phys. Rev.* **181**, 1278 (1969).
34. D. van der Marel, J. L. M. van Mechelen, and I. I. Mazin, “Common Fermi-liquid origin of T^2 resistivity and superconductivity in n-type SrTiO_3 ”, *Phys. Rev. B* **84**, 205111 (2011).
35. Z. Ergönenc, B. Kim, P. Liu, G. Kresse, and C. Franchini, “Converged GW quasiparticle energies for transition metal oxide perovskites”, *Phys. Rev. Materials* **2**, 024601 (2018).
36. L. Hedin, “New Method for Calculating the One-Particle Green’s Function with Application to the Electron-Gas Problem”, *Phys. Rev.* **3A**, A796 (1965).
37. W. Meevasana, X. J. Zhou, B. Moritz, C.-C. Chen, R. H. He, S.-I. Fujimori, D. H. Lu, S.-K. Mo, R. G. Moore, F. Baumberger, T. P. Devreux, D. van der Marel, N. Nagaosa, J. Zaanen and Z.-X. Shen, “Strong energy-momentum dispersion of phonon-dressed carriers in the lightly doped band insulator SrTiO_3 ”, *New Journal of Physics* **12**, 023004 (2010).